

The Investigation Thermal Efficiency of High Performance Fiber Reinforced composites with additive Multi-Wall Carbon Nanotubes

Adar Karagöz

AVA construction, The Graduate School of Natural and Applied Sciences, Dokuz Eylul University, Paris, France

Corresponding author

Adar Karagöz, AVA construction, The Graduate School of Natural and Applied Sciences, Dokuz Eylul University, Paris, France

Submitted: 25 Feb 2020; Accepted: 06 Mar 2020; Published: 20 Mar 2020

Abstract

Every year thousands of traffic accidents occur due to icing of roads which challenge lives and property. In this study the suitability of steel fibers and multi wall carbon nano tube (MWCNT) for electrical (Joule) heating was determined by cluster heating test which is novel for the literature.

In this study, the bearing elements of the buildings and roads are intended to be a heater. Experiments were tested for a total of four weeks, once every week. During the tests, the top surface temperature, the voltage supplied and the current were recorded. The temperature increase and temperature increase rate were determined. Mortar having MWCNT ratio showed a superior heating performance for 4 weeks. In this study, the bearing elements of the buildings and roads are intended to be a heater. The thermal efficiency of the high performance fiber reinforced composites were investigated.

Keywords: Self-heating, Multifunctional Smart Material, Electrical Heating, Cement, Multi- wall Carbon Nanotube

Introduction

Pavement and runway icing is a major challenge for highway and air transportation. Numerous accidents due to icing causes loss of lives, injuries and damage to property.

In USA, more than 1300 people lose their lives and 116,800 people get injured annually due to snowy- slushy-icing pavements while 900 people are killed and 76,000 people get injured in accidents during snowfall and sleet. Besides, winter road maintenance costs are 20% of state DOT maintenance costs. More than 2.3 billion dollars (USD) were spend by state and local agencies for snow and ice controls on pavements annually; while millions of dollars are spend by road agencies to repair infrastructure damage caused by snow and ice [1]. The projection of the problem to whole world ends up with considerable loss and cost.

In Turkey, during 2006-2007 winter, 50422 tons of salt was used for deicing roads [2]. Salt is detrimental for concrete [3]. Use of salt and other deicers on asphalt degrades the mechanical properties [4-8]. The salt and other deicers corrode the vehicles, pollute the soil and underground water sources.

The chemicals used for deicing of runways at airports are detrimental for the runway, for the aircraft and environment. Organic salts (potassium formate and acetate, etc.), oxidizes the carbon in brakes

which challenges safety while damaging the body, electric cables and landing gear [9-11]. Moreover, the runways deicers are sprayed by wheels during takeoff and landing to wings which had anti-icing agent. The anti-icing agent loses its function when runway deicer is mixed with it which dangers the aircraft due to icing during flight [12].

Applied DC current to nickel particle reinforced cement based composites and reported that the composite was heated [13]. Carbon fiber reinforced mortar was heated by applying electric current [14]. It was reported that the cement composite with steel fiber of 8 μm , 0.7 volume % had resistivity of 0.85 Ohm.cm and was heated when electric current was applied [15,16]. Gomis et al., reported that cement composites reinforced with carbonaceous materials were able to heating by electric current [17]. Galao et al., tested carbon fiber reinforced concrete with electrical heating test [18].

Fiala et al., reported that alkali-activated aluminosilicates with carbon black can be improved for self-heating material technology [19]. Kim et al., stated that cement composites with CNT less than 0.6% by weight is appropriate for self-heating [20]. Galao et al., stated that shotcrete of carbon nano fiber reinforced cement paste (5% by cement mass) had electrical heating performance [21].

Materials and Methods

Cem II 42,5R type cement and the fine aggregate (0-5mm) were used. In the mixture, plasticiser was used. Stainless steel wire mesh was used as electrode. brass fiber was used as conductive additive.

According to the information given by the producer (LANXESS), Characteristic of MWCNT Rhenofit® CNT-3 is a water-based dispersion of single wall carbon nanotubes (MWCNT) which can be used directly for production of formulations. The dispersion is highly homogeneous and stabilized and the applied process ensures non-destructive dispersing of carbon nanotubes under mild conditions. Characteristic properties of MWCNT are presented in table as obtained from the producer:

- Composition: 2 wt% multi wall carbon nanotubes 2 wt% low molecular weight dispersing agent 96 wt% water
- Appearance: Black dispersion
- Odour: No odour
- Compatibility: Can be mixed with liquid systems and appropriate polar organic solvents
- pH value: Slightly basic (approximately pH = 8-10).

Cement and aggregates were put in mixer. Water with MWCNT and plasticizer were weighed in separate cups then mixed in a cup. Water and plasticizer mix were added to dry aggregate and cement in 3 stages and mixed every time.

Mixture was cast into the molds in 2 stages. The mix was rodded 10 times. Mold with mixture were vibrated on a vibration table. After 24 hours, sample was demolded and cured in room temperature (20°C) water for 28 days. Mold size was 10 × 10 × 3.5 cm³. Mold size was 10 × 10 × 3.5cm³.

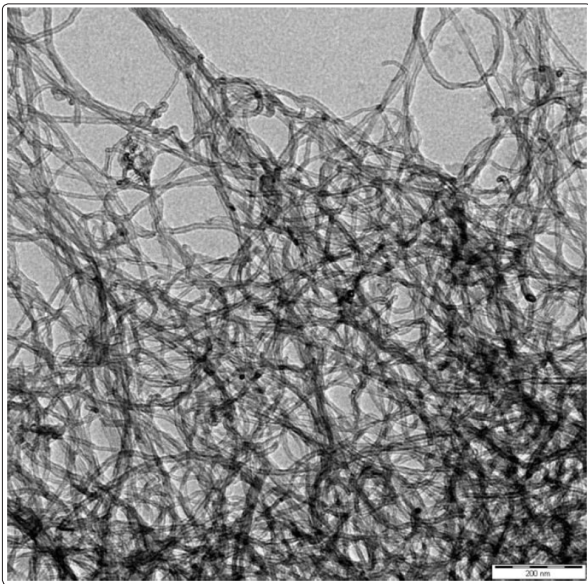


Figure 1: SEM image of MWCNT (Scale is 200 nm)

The mixtures were designed according to TS 802 “Design of Concrete Mixtures” standard. In this study, concrete were designed which had 3% volume of brass fiber.

Three 10 × 10 × 3.5 cm prismatic sample from each mixture were tested. Experiments of the sample was made on 35th of production. A thermal camera was recorded during the experiment. A direct current source was used. The test diagram and experiment are presented in Figure 2, 3. During the electrical heating test, direct current was supplied from the two electrodes to the sample with the DC source. To measure the electrical resistivity of the samples, the sample potential differences (Vs) were measured from both electrodes.

Current passing through the circuit (I) and the potential difference (Vs) was recorded. The instantaneous electrical resistance (Rs) of the sample using Ohm's law was calculated by using Equation 1.

$$R_s = (V_s) / (I) \quad (1)$$

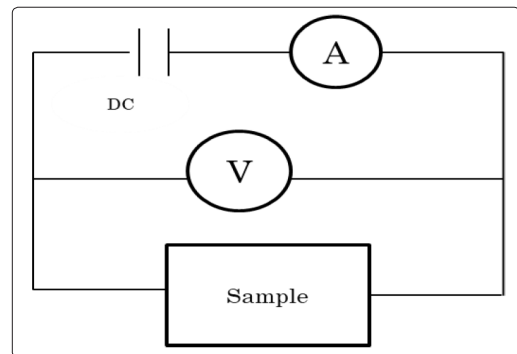


Figure 2: Circuit diagram

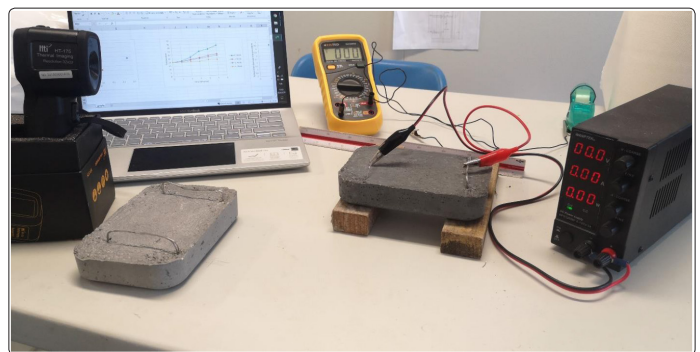


Figure 3: Concrete and Schematic of Experiment

Results and Conclusions

This experimental study is trying to solve the heating problem by means of a concrete system that can be heated by electricity. The concrete was tested once a week for a total of 4 weeks under 112V voltage. In addition, total experiment time was determined as 5 minutes and the results were recorded. It has been observed that a sample reached high temperature in a very short time. After first week experiment, it has been observed that current and temperature increase getting decrease every week.

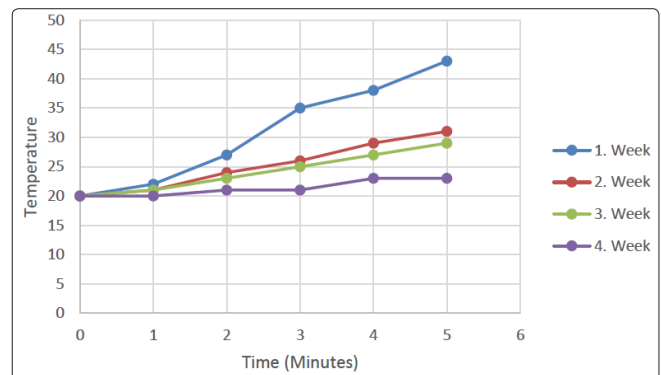


Figure 4: Temperature-Minute Graphs

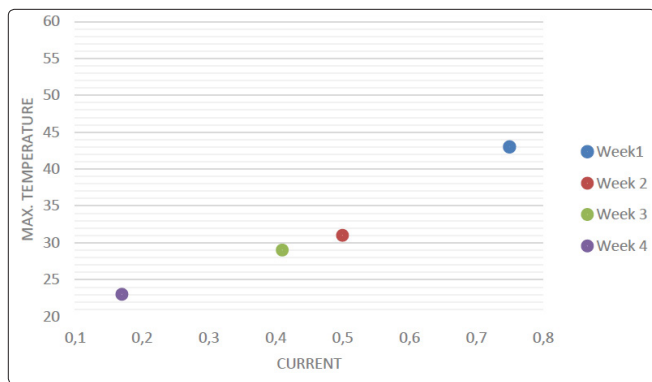


Figure 5: Max. Temperature-Current Graph

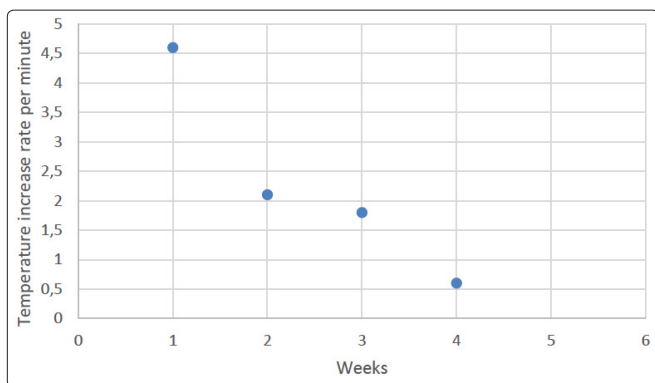


Figure 6: Temperature increase rate per minute

In this study cement matrix composite was designed. Designed with MWCNT and 3 percent of brass fiber. Sample was prepared, cured and tested. The effect of electrical conductivity, the amount of temperature increase per minute were experimentally tested. Important results are presented as below;

The temperature-time curves obtained from the 112V electrical heating tests are given in

- There was almost a non-linear relation among the temperature increase and temperature increase is the same every week.
- The temperature rise is the MWCNT ratio, have different temperature increases every week.
- The temperature rise rates are the MWCNT ratio, have decreasing every week.
- The mixture of MWCNT, the temperature increase and temperature increase rates are decreasing every week.

The MWCNT cement can be develop as electrical-heating cement but it need to observe the relation of humidity-temperature increase and also whether there is damage caused by voltage should be examined with a microscope.

Acknowledgements

I would like to thank to LANXESS company for supplying Single Wall Carbon nanotube and Multi Wall Carbon nanotube.

References

1. US DOT (2018) https://ops.fhwa.dot.gov/weather/weather_events/snow_ice.htm. 28/8/2018
2. General Directorate of Highways (2008) The maintenance and operating costs of state and city roads for 2007. Transportation and Cost Analyses Directorate report, Ankara, in Turkish.
3. Mehta PK, Monteiro PJM, Concrete, Mc Graw Hill, 2006.
4. Amini B, Tehrani SS (2014) "Simultaneous effects of salted water and water flow on asphalt concrete pavement deterioration under freeze-thaw cycles", *Int Jour of Pavement Engineering* 15: 383-391.
5. Tang N, Sun CJ, Huang SX, Wu SP (2013) "Damage and corrosion of conductive asphalt concrete subjected to freeze-thaw cycles and salt", *Materials Research Innovations* 17: 240-245.
6. Ozgan E, Serin S, Gerengi H, Arslan İ (2013) "Multi-faceted investigation of the effect of de-icer chemicals on the engineering properties of asphalt concrete", *Cold Regions Science and Technology* 87: 59-67.
7. Feng D, Yi J, Wang D, Chen LL (2010) "Impact of salt and freeze-thaw cycles on performance of asphalt mixtures in coastal frozen region of China" *Cold Regions Science and Technology* 62: 34-41.
8. Hassan Y, El Halim AOA, Razaqpur AG, Bekheet W, Farha MH (2002) "Effects of runway deicers on pavement materials and mixes: Comparison with road salt" *Jour of Transportation Engineering-ASCE* 128: 385-391.
9. European Aviation Safety Agency (EASA) (2016) "Catalytic Oxidation of Aircraft Carbon Brakes due to Runway De-Icers". Safety Information Bulletin (SIB) 2008-19R2.
10. Shi X (2008) Impact of Airport Pavement Deicing Products on Aircraft and Airfield Infrastructure. Washington DC: Transportation Research Board.
11. Arriaga M "Effects of Alkali Metal Runway Deicers on Carbon Brakes". Boeing AERO magazine Q1/2014.
12. European Aviation Safety Agency (EASA) (2010) "Potential Performance Degradation of Anti-icing Fluids- Reduced Holdover Times". EASA Safety Information Bulletin (SIB) 2010-26.
13. Zhang K, Han B, Yu X (2011) "Nickel particle based electrical resistance heating cementitious composites", *Cold Regions Science and Technology* 69: 64-69.
14. Gopalakrishnan K, Ceylan H, Kim S, Yang S, Abdulla H (2015) "Electrically Conductive Mortar Characterization for Self-Heating Airfield Concrete Pavement Mix Design", *Int J Pavement Res Technol* 8: 315-324.
15. Chung DDL (2004) "Self-heating structural materials", *Smart Materials and Structures* 13: 562-565.
16. Wang S, Wen S, Chung DDL (2004) "Resistance heating using electrically conductive cements", *Advances in Cement Research* 16: 161-166.
17. Gomis J, Galao O, Gomis V, Zornoza E, Garcés P (2015) "Self-heating and deicing conductive cement. Experimental study and modeling", *Const Build Mater* 75: 442-449.
18. Galao O, Baeza FJ, Zornoza E, Garcés P (2014) Self-heating function of carbon nanofiber cement pastes. *Materiales de Construcción* 64.
19. Fiala L, Jerman M, Rovnanik P, Cerny R (2017) Basic Physical, Mechanical and Electrical Properties of Electrically Enhanced Alkali-Activated Aluminosilicates. *Materials and Technology* 51: 1005.

-
20. Kim GM, Naeem F, Kim HK, Lee HK (2016) Heating and heat-dependent mechanical characteristics of CNT-embedded cementitious composites. *Composite Structures* 136: 162-170.
21. Galao O, Banon L, Javier BF, Carmona J, Garcés G (2016) “Highly Conductive Carbon Fiber Reinforced Concrete for Icing Prevention and Curing”. *Materials* 9.

Copyright: ©2020 Adar Karagöz. This is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution, and reproduction in any medium, provided the original author and source are credited.